See discussions, stats, and author profiles for this publication at: https://www.researchgate.net/publication/318055355

Understanding the Nature and Characteristics of Dark-Black Stains on Rooftops in Uyo Metropolis-Nigeria 1

reads 189

Article · July 2017

DOI: 10.2412/mmse.95.14.172

citations 0	
1 author	
	Aondona Paul Ihom University of Uyo 42 PUBLICATIONS 145 CITATIONS
	SEE PROFILE

Some of the authors of this publication are also working on these related projects:

Project

development of polyester matrix natural fiber reinforced composite View project

Effect of electrode composition on the microstructure and mechanical behaviour of micro-alloyed steel weldment View project

All content following this page was uploaded by Aondona Paul Ihom on 01 July 2017.

Understanding the Nature and Characteristics of Dark-Black Stains on Rooftops in Uyo Metropolis-Nigeria

Ihom A.P.¹, Uko D.K.¹, Markson I.E.¹, Eleghasim O.C.¹

1 - Department of Mechanical Engineering, University of Uyo, Uyo, PMB, Uyo, Nigeria

a – <u>ihom@uniuyo.edu.ng</u>



Keywords: understanding, environmental pollution, nature, characterization, dark black stains, Uyo.

ABSTRACT. Understanding the Nature and Characteristics of Dark-Black Stains on Roof-Tops in Uyo Metropolis-Nigeria; a study aimed at knowing the nature and characteristics of dark black stains on rooftops in Uyo metropolis has been undertaken. The study which covered key areas of the town, involved taking samples from rooftops, these samples were sent out for tests using Energy Dispersive X-Ray Fluorescence (ED-XRF), Optical Emission Spectrometer (OES), X -Ray Diffractometer (XRD) and Scanning Electron Microscope (SEM). The tests were carried out on the dark black stains which were scrapped from the rooftops. Tests were also carried out on the sheets, which were directly cut from the roofs. The work was able to establish that the dark black stains on the roofs can be cleaned using soft brush and water. The results of the work equally provided the nature and characteristics of the dark black stains on the surface of roofs in Uyo metropolis. The major components of the dark black stains are alumina (16%), silica (43.80%), carbonaceous and volatile organic matter (16.59%), iron oxide (heamatite) (10.55%), potassium oxide (3.20%), titanium oxide (2.93%) and sulphite (SO₃) (2.71%). The SEM micrographs gave the structure of the dark black stains which were scrapped from the roofs, the structure revealed small shinny white particles, amorphous molecular structure similar to that of polymers and a crystal structure which resembles that formed by carbon and silica. The SEM micrographs also show how the stains are formed on aluminium and zinc substrate. The nature and characteristics of the dark black stains have indicated that using water from these rooftops for direct consumption purpose may have some health implications, and relevant government agencies are requested to investigate the health implications.

Introduction. In an address presented by the governor of Akwa Ibom State, Mr Udom Emmanuel Gabriel at the environment summit organized by the state government at Le Meridien Hotel and Golf Resort, Uyo. The governor lamented the adverse effects of environmental pollution caused by oil flaring and fossil fuels combustion on humans and the environment, he specifically mentioned darkening rooftops in Uyo metropolis which has taken away the aesthetics of many buildings in the state. According to the governor, the problem is so serious that many people are now using dark and black coloured roofing sheets to conceal the black deposits on their roof-tops. The nature of this black deposit is not understood, it is only assumed that it is from gas flaring and combustion of fossil fuels from generators and automobiles. Olajire [13] and Nkwocha [11] also in their respective studies have linked the dark black stains on the roofs to pollution from gas flaring and other industrial activities. Fig. 1-5 clearly captures the menace.

[@] 2017 The Authors. Published by Magnolithe GmbH. This is an open access article under the CC BY-NC-ND license http://creativecommons.org/licenses/by-nc-nd/4.0/



Fig. 1. Building in Uyo Metropolis: The Roof is Completely Covered with Dark-Black Deposit.



Fig. 2. Building Roof Completely Covered with Dark-Black Coating/Deposit.



Fig. 3. Building Roof Completely Covered with Dark-Black Deposit.



Fig. 4. The Roof Top of the Building in the Front is covered with Dark-Black Deposit, the Storey Buildings Behind are Roofed with Dark-colour Roofing Sheets to Conceal the Effect of the Dark-Black Deposit.



Fig. 5. Dark-Black Deposit on Colour Roofs in a Housing Estate in Uyo Town.

Environment means the surroundings in which we live. It is a life-sustaining system in which various living beings like animals, including man, birds, insects, micro-organisms like algae, fungi, protozoa, amoeba and non-living beings like air, water, and soil are inter-related. From time immemorial, the biosphere is discharging faithfully its duty of recycling waste products to make good the loss so that every generation finds it the same as the one before it. According to [2] this self-cleaning and equilibrium maintenance of the biosphere is disastrously disturbed, if waste products released into it exceed its capacity to purify herself. Of late, this is what is happening. We load it with enormous amounts of waste product that the biosphere is becoming more and more poisonous and soon a day will be reached when it becomes inhabitable. When air is polluted, it carries the pollutant with it along the way some of the pollutants are deposited on things with which it comes into contact with. Living things also inhales the polluted air. When it rains the rain washes the pollutants unto roof-tops and down to the soil this explains the interrelationship mentioned above by [2]. Tice [15], Okedere and Elehinafe in their respective works have addressed the effect of air pollution from various sources and associated side effects on structures and living things.

Primitive man ate uncooked food available from plants, birds or animals within his reach. He ate the raw meat. He drank the water from the rivers. He lived in caves or huts made of mud, wood and leaves of some trees. This sort of living never polluted the environment. When Promethenes stole fire, man's travails began. He used it not only to cook food but also as a weapon to destroy the neighbour-hood. With fire, smoke issuing out was polluting the atmosphere; there was stink. It was in the beginning of the first century that the Roman philosopher Sceneca complained about air pollution. This went on increasing until in the 20th century the Ganges became a death bed for all aquatic animals and the series of air pollution disasters affected millions all over the world [2].

Buildings in Uyo metropolis shortly on completion, the roof gets covered up with dark-black deposits. For reflective roofing sheets they cease to be reflective as a result of this deposits. Jordan Woods [18] of the Berkeley Laboratory notes that reflective roofs are needed for cool buildings [18]. Aesthetics is very important in building structures; aesthetics is now being taken away in most structures shortly after completion by this menace, which requires thorough investigation in order to be able to tackle it. The menace may even have health implication in which case the findings may be of value to the Federal Ministry of Health. In a recent publication by Ihom [5] and [6] the authors observed that WHO has released a report which said that air pollution has become worse in many cities around the world in recent years, especially in Africa and South-East Asia. The UN agency's report showed that nearly 90 per cent of the world population breathes air that is markedly above the limits recommended by the WHO. Experts from the agency identified car traffic, the burning of coal, oil and gas as well as badly insulated houses as the main culprits. The UN agency had said in April, 2012 that polluted air killed 3.7 million people under the age of 60 in 2012 [17]. Similarly in a publication by Ola [12] the authors observed after their work, which was aimed at indexing pollution in Jos Metropolis that the levels of H₂S, Carbon monoxide and particulate matter were above specified limits for quality air and therefore had some health implications on humans. Understanding the nature of this deposit, which obviously is from the air is therefore very important.

The preceding forms the objective of this work, which is to understand the nature of the dark-black deposits on the surface of roof-tops in Uyo metropolis. The project is part of an Institutional Based Research Work sponsored by Tertiary Education Trust Fund (TETFUND) and it is ongoing.

Materials and method

Materials and Equipment. The materials used for this work included; samples of the dark-black deposits scrapped from roof-tops, samples of test specimens taken from zinc-plated roofing sheet covered with the deposit, samples of test specimens taken from aluminium roofing sheet, and water. The equipment used included; sample cutting scissors, test specimen plastic containers, roof climbing ladder, scrapping tools, Energy Dispersive X-Ray Fluorescence (ED-XRF), Scanning Electron Microscope (SEM), Shimadzu X-ray Diffractometer (XRD) and Optical Emission Spectrometer (OES). Others included, bucket, soft brush and imaging device.

The Study Area. The study area of this research work is Uyo metropolis. Uyo is the Capital of Akwa Ibom state. It is a major oil producing state in Nigeria, with a lot of gas flaring activities going on from the oil exploiting companies. The population of Uyo according to the 2006 Nigerian census which comprises Uyo and Itu is 436,606. The metropolitan area covers an estimated area of 168 km² (65sq.mi). Uyo is a fast-growing city and has witnessed some infrastructural growth in recent years. It is located on coordinates $5^{0}2$ `N and $7^{0}56$ `E.

The average annual rainfall in the study area is between 2000-4000mm with the period of fall usually between April and October. The rainfall reaches its peak in the months of June and September, while the dry period falls between November to March. The relative humidity of the area varies between 75% and 95% with mean annual temperatures of about 26 to 36°C. Fig. 6 is the map of the study area. The samples for the work were taken in different areas of the metropolis covering, Use Offot on Nwanniba road, University of Uyo, main campus on Nwanniba road, Ikot-Okubo on Abak road and Mbaibong on Oron road. The town is characterized by high usage of generators as a result of incessant power failure from the national grid and high vehicular traffic typical of a growing metropolis.

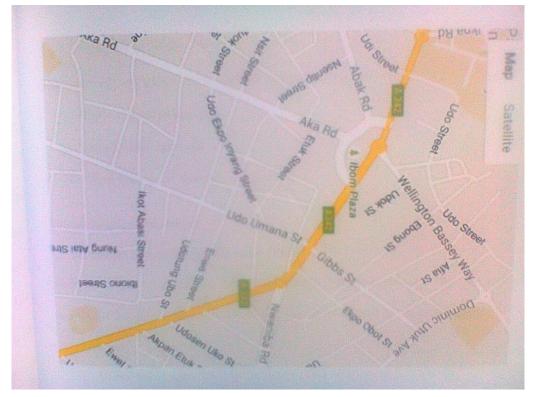


Fig. 6. The Map of Uyo Metropolis the Study Area.

Method. Sample test specimens were taken from roof –tops of buildings in different parts of Uyo metropolis as indicated in the study area above. The samples which were taken included the dark-black coating on top of roofs, which was scrapped from the roof and labeled No1, dark-black coating on zinc coated roofing sheet, labeled No2, and dark-black coating on aluminium base roofing sheet, labeled No3. The last two were cut directly from the roof, see Fig. 9-10. These specimens were sent to National Steel Raw Materials Exploration Agency, Kaduna, Defence Industries Corporation of Nigeria (DICON), and National Metallurgical Development Centre, Jos for analysis. To determine the nature of the dark-black deposit on roof-tops in Uyo-metropolis. Compositional tests were carried out using Shimadzu X-ray Diffractometer (XRD) made in Japan, mini Pal4 ED-XRF (Energy Dispersive X-ray Fluorescence) and Optical Emission Spectrometer (OES). The microstructure of the deposits on the surface of the roof-tops was carried out using Scanning Electron Microscope (SEM).

Critical examinations of the roofs were also carried out using visual examination to ascertain the nature of the deposit and also to establish whether it was living things growing on the roof. Remedial steps were taken to remove the dark-black coating from the roof by cleaning with water and soft brush (See fig. 7-8. No chemical was used for the cleaning, since there was no chemical reaction between the deposits and the roof base. The dark-black deposit was stuck to the roof purely by adsorption, which upon cleaning revealed a clean-shining surface of the roof. See fig.7. Only few growths were seen on the roofs and where they existed the zinc coating was eroded and accompanied by corrosion. The colour of the growth was also different from that of the dark-black deposit.



Fig. 7. Field Work and Sample taking in Progress.



Fig. 8. Roofs showing Reflective Surfaces where test specimens were scrapped from the roofs.



Fig. 9. Transferring Test Samples to Plastic Containers.

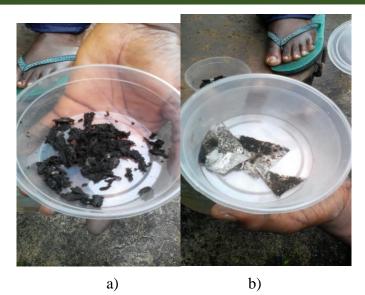
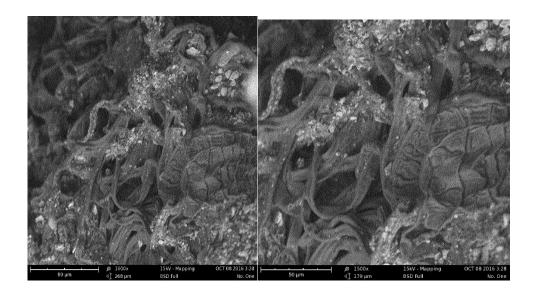


Fig. 10. Dark-Black Material Scrapped in (a), Test Specimens cut from the roofs in (b).

Results and discussion

Results. The result of the work is as presented below: Scanning Electron Microscope (SEM) Micrographs



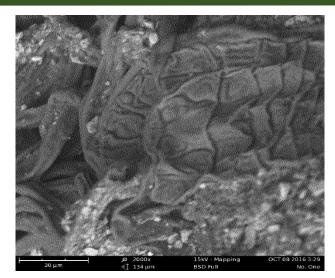


Fig. 11. Scanning Electron Microscope (SEM) Micrographs of the Scrapped Coatings on the Rooftops of Buildings at different magnifications (1000X, 1500X, 2000X).

The micrograph on the Fig. 11 shows that the dark-black material is not a uniform material; small white particles are there, amorphous-like structure like that of the polymer material can be seen and crystal-like structure similar to that seen in some carbon forms can be seen.

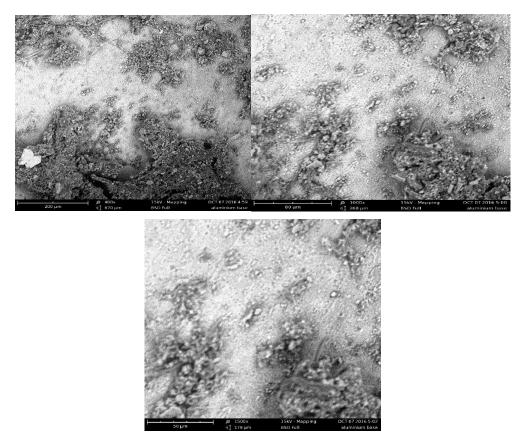


Fig. 12. Scanning Electron Microscope (SEM) Micrographs of dark-black Deposit on Aluminiumbase roofing sheet at different Magnifications (400X, 1000X, 1500X). The light shining areas are where the deposit of the material is low and the dark areas are where the deposit has covered the aluminium sheet completely.

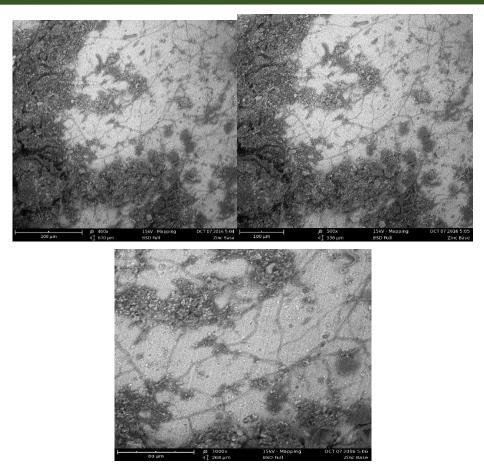


Fig. 13. Scanning Electron Microscope (SEM) Micrographs of dark-black Deposit on Zinc-Coated base roofing sheet at different Magnifications (400X, 500X, 1000X). The light areas have low deposit of the material; the substrate is still shining and the dark areas have large deposit of the material; the substrate is covered.

Chemical Analysis Using ED-XRF

Table 1.	Chemical	Composition	of Da	ark-Black	Material	Scrapped	from	Roof-Tops	(Analysed	at
DICON).	Paramete	rs (in %).								

S /No	Sample	Al ₂ O ₃	SiO ₂	P2O5	SO ₃	K ₂ O	CaO	TiO ₂	V2O5
1	Blackish powder from rooftop	24.10	46.00	1.5	3.16	2.81	1.5	2.48	0.11

Cr ₂ O ₃	MnO	Fe ₂ O ₃	NiO	CuO	ZnO	Yb ₂ O ₃	Re ₂ O ₇	Ag ₂ O	Eu ₂ O ₃
0.034	0.15	14.49	0.02	0.11	0.15	0.06	0.19	2.87	0.23

Table 2. Chemical Composition of Dark-Black Material Scrapped from Roof-Tops (Analysed at NMDC Jos). Parameters (in %).

S/No	Sample	Al ₂ O ₃	SiO ₂	P2O5	SO ₃	K ₂ O	CaO	TiO ₂	V2O5
1	Blackish powder from roof-top	16.00	43.80	1.20	2.71	3.20	1.62	2.93	0.11

Cr ₂ O ₃	MnO	Fe ₂ O ₃	NiO	C02O3	CuO	ZnO	Br	Rb ₂ O	SrO
0.10	0.31	10.55	0.05	ND	0.09	0.22	0.07	0.03	0.05

ZrO ₂	Yb ₂ O ₃	Re ₂ O ₇	PbO	Carbonaceous matter	and	volatile
0.20	0.001	0.06	0.11	16.59		

X-Ray Diffractometer (XRD) Analysis Result on Dark-Black Material Scrapped from Roof-Tops (Analysed at NSRMEA, Kaduna)

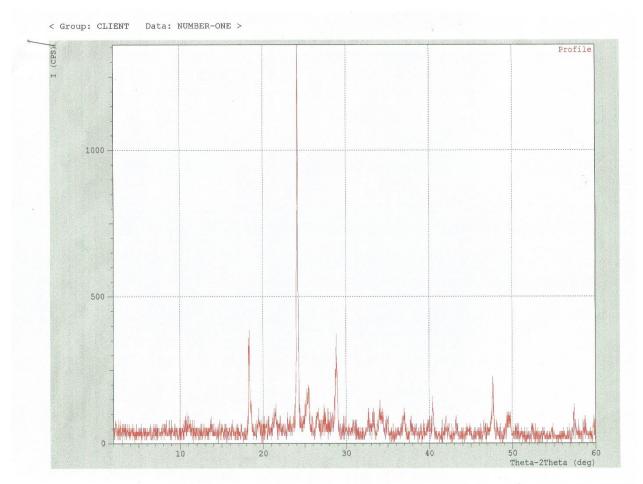


Fig. 14. X-Ray Diffractometer Plot of Intensity against Theta-2Theta for the Dark-Black Material from the Roof-Tops.

							12
	* * * * * * *	SEARCH /	MATCH I	RESULT	*******		
Group Name : CL Data Name : NU	IENT MBER-ONE						
	MBER-ONE.PS	E					
Sample Name :							
Comment : DA	RK-BROWN						
<entry card=""></entry>							
	hemical For		Mana	S	L	d. I	R
1 51-1890 K2Ti2	hemical Nam 05	e (Mineral	Name)	0.331.0.	Dx 643(9/15)	WT% S.G. 0.730 0.808	0 379
	tassium Tit	anium Oxid	e	0.001 0.			
2 21-1272 TiO2				0.114 0.	714(5/39)	0.783 0.658	0.368
and the second s	tanium Oxid	e (Anatas	e, syn)				
3 47-2217 (C2F4			- 1	0.259 0.	400(4/12)	0.748 0.729	
4 35-0816 CaF2	ly(tetraflu	oroechyten	e)	0.041 0.		0.552 0.437	
	lcium Fluor	ide (Fluo	rite, sy	yn)			
5 39-1352 Zn3 (P						0.686 0.456	
	nc Phosphat	e Hydrate	(Paraho	-			
6 21-1276 TiO2	tanium Oxid	e (Rutile	syn)	0.060 0.	429(3/38)	0.659 0.597	
7 26-1079 C	ouniton onto		/ 0111 /	0.111 0.	600(3/16)	0.745 0.360	0.161
Ca:	rbon (Grap	hite-3\ITR	\RG, syr	n [N)			
8 16-0613 Mgx (Mg							
			Silicat	te Hydroxid		0 700 0 000	
9 10-0492 KMg3(minum Si	0.204 0. Llicate Hyd		0.700 0.228	
10	cassian nay	neoran nru	million Di				
***	Basic Data	Process	***				
Group : C	LIENT						
Data : N	UMBER-ONE						
# Strongest 3		d	1/11	FWHM	Intereity	Integrated	Tot
no.	2Theta (deg)	(A)		(deg)	(Counts)	(Counts)	101
1 16 2 6	24.1893 18.3839	3.67637 4.82214	100	0.15350 0.19720	134 30	1224 291	
3 28	28.8474	3.09245	19	0,25500	2.6	340	
# Peak Data L peak	ist 2Theta	d	I/I1	FWHM	Intensity	Integrated	Int
no.	(deg)	(A)		(deg)	(Counts)	(Counts)	
1 2	2.6792	32.94936 8.22901	4	0.09330 0.07670	5 5	30 28	
3 4	14.8404 16.3963	5.96460 5.40194	3	0.09000	4 4	32 48	
5	17.4641 18.3839	5.07398	3 22	0.07000	4 30	22 291	
7	18.6272	4.75970	7	0.12000	9	70	
8	19.5143 20.7208	4.54528 4.28327	4 3	0.10000	6 4	60 43	
10	21.2344 21.3989	4.18081 4.14904	4 3	0.05000	5 4	16 22	
12	21.5386	4.12245	5	0.10000	7	43	
13	22.1022 22.9585	4.01858 3.87060	4 3	0.07000	5 4	29	
15 16	23.2546 24.1893	3.82198 3.67637	3 100	0.08000 0.15350	4 134	19 1224	
17	25,1108	3.54351	5	0.08000	7	35	
18 19	25.2905 25.4901	3.51873 3.49163	8 9	0.09000 0.14660	11 12	61 106	
20 21	26.0225 26.3287	3.42139 3.38229	3 3	0.06670	4	14 15	
22 23	26.5284 26.6781	3.35728 3.33878	5	0.20000	777	68 54	
24	27.3071	3.26329	4	0.08000	5	36	
25	27.4719 28.4255	3.24408 3.13738	4 3	0.05000	5	23 24	
27 28	28.6252 28.8474	3.11595 3.09245	8 19	0.10000 0.25500	11 26	50 340	
29	29.9034	2.98560	3	0.08000	4	25	2.1
30 31	30.9472 31.1020	2.88724 2.87322	3	0.09000	4	22 12	
32 33	32.6203 32.7401	2.74287 2.73311	3 3	0.06000	4 4	43	
34	33.2621	2.69140	5	0.08500	7	46	
35 36	33.8340 34.0188	2.64721 2.63325	36	0.09000	4 8	20 42	
37 38	34.1787 34.3585	2.62129 2.60799	4	0.16000 0.12000	5 6	39 40	
39 40	35.0179 36.9961	2.56037 2.42788	4	0.10000	6	35 75	
41	37.7705	2.37986	3	0.05000	4	22	
42 43	39.3243 39.9689	2.28934 2.25389	3 4	0.10000	4 5	26 23	
44 45	4D.4386 41.9975	2.22879 2.14959	9	0.13000	12 6	89 67	
46	42.2524	2.13721 2.09195	3	0.08000	4 7	36	
47 48	43.2118 47.4894	1.91302	53	0.08000	4	0	
49	47.6343 48.1491	1.90754 1.88834	13	0.17000 0.08000	17 4	161 22	

Fig. 15. X-Ray Diffractometer (XRD) Analysis Result on Zinc Coated Roofing sheet Covered with Dark-Black Material (Analysed at NSRMEA, Kaduna).

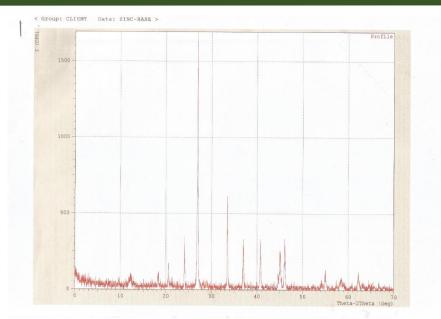


Fig. 16. X-Ray Diffractometer Plot of Intensity against Theta-2Theta for the Zinc Coated Sheet Covered with Dark-Black Material.

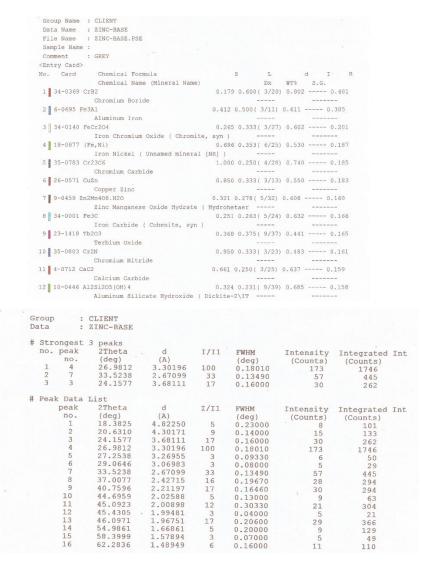


Fig. 17. X-Ray Diffractometer (XRD) Analysis Result on Aluminium Alloy Roofing Sheet Covered with Dark-Black Material (Analysed at NSRMEA, Kaduna).

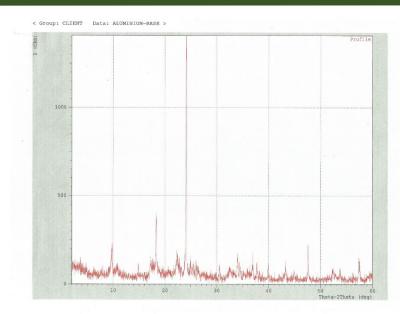


Fig. 18. X-Ray Diffractometer Plot of Intensity against Theta-2Theta for the Aluminium Roofing Sheet Covered with Dark-Black Material.

Gro Dat	a :	CLIENT ALUMINIUM-I	BASE					
# s	trongest	3 peaks						
n	no. peak	2Theta	d (A)	1/11	FWHM (deg)	Intensity (Counts) 227	Integrated	Int
	1 13 2 6	24.1362 18.3653	(A) 3.68434 4.82698 1.90760	100	(deg) 0.15110 0.15540	227	1943	
	3 31	47.6327	1.90760	15	0.12220	35	250	
# P	eak Data	List 2Theta	d	1/11	FWIIM	Intensity	Integrated	Tet
	no. 1	(deg)	(A)		(deg)	(Counts)	(Counts)	inc
	2	9.7615 9.9003	9.05360 8.92698	10	0.09340 0.18280	16 22	112 194	
	3	14.9284 17.2296	5.92964 5.14251	5	0.10670	11 10	102 64	
	5	17.3693 18.3653	5.10146	4	0.13340	10	92	
	7	22.1571 22.3716	4.00875	4	0.12000	8	67	
	9	22.6359	3.92503 3.89454	3	0.23000			
	10 11	22.8155 23.1623	3.89454 3.83700 3.73972	4	0.12000 0.06500	8 9 7	64 50	
	12 13	23.7735 24.1362	3.73972	3	0.05000 0.15110	7 227	32 1943	
	14 15	24.9816 25.4926	3.68434 3.56154	5	0.10900	12	77	
	16	26.0691	3.49130 3.41538 3.37663	4	0.08500	9 9	56	
	17 18	26.3736 30.5542			0.11000	7 15	91 114	
	19 20	30.7590 32.4105	2.90448	4	0.07330	8	41	
	21 22	34.0421	2.63150	8	0.16670	19	167	
	23	34.4292 34.5916	2.63150 2.60279 2.59094 2.43130	6 4 7	0.09170	13 10	65 50	
	24 25	36.9422 37.7870	2.43130 2.37886	7	0.18210	16 14	140	
	26	38.2551	2.43130 2.37886 2.35082 2.25528 2.24198 2.08866 2.01466	4 7	0.09340	8	83 44 114	
	28	40.1903 43.2833	2.24198	3	0.11470 0.07330	17 7	32	
	30	44.9583	2.08866 2.01466 1.90760	4	0.12330 0.11500	17 8	155 63	
	31 32	47.6327 52.3272	1.90760 1.74697 1.74264	15 4 4	0.12220 0.10000	35 10	250 68	
	33	52.4671 53.7649	1.74264 1.70359	4	0.10000	8	64	
	35	57.4372	1.60309		0.14330 0.13600	10 25	93 201	
Group Name	35	57.4372	1.60309					
Group Name Data Name	35 CLIE	57.4372	1.60309					
Data Name	35. : CLIE : ALUM	57.4372 ENT HINIUM-BASE	1.60309					
Data Name File Name Sample Name	35. : CLIE : ALUM : ALUM e :	57.4372 ENT HINIUM-BASE HINIUM-BASE	1.60309 .PSE					
Data Name File Name Sample Name	35. : CLIE : ALUM : ALUM e :	57.4372 ENT HINIUM-BASE HINIUM-BASE	1.60309 .PSE					
Data Name File Name Sample Name Comment Entry Card	35 : CLIE : ALUM : ALUM e : : GREY	57.4372 NT NINIUM-BASE NINIUM-BASE NISH SAMPLE	1.60309 .PSE	11	0.13600	25	201	
Data Name File Name Sample Name Comment Entry Card	35 : CLIE : ALUM : ALUM e : : GREY	57.4372 NT NINIUM-BASE NINIUM-BASE NISH SAMPLE	1.60309 .PSE	11	0.13600	25	201	I
Data Name File Name Sample Name Comment Entry Card D. Card	35 : CLIE : ALUM : ALUM e : : GREY	57.4372 NT NINIUM-BASE NINIUM-BASE NISH SAMPLE	1.60309 .PSE	11	0.13600	25	201	I S.G.
Data Name File Name Sample Name Comment Entry Card D. Card	35 : CLIE : ALUM : ALUM e : : GREY	57.4372 NT NINIUM-BASE NINIUM-BASE NISH SAMPLE	1.60309 .PSE	11	0.13600	25	201	I S.G. .874 0.4
Data Name File Name Sample Name Comment Entry Card 5. Card 1 35-0787	35 : CLIE : ALUM : ALUM : ALUM : GREY Che Che Mo2C Moly	57.4372 NT NINIUM-BASE NINIUM-BASE NISH SAMPLE	1.60309 .PSE	11 Name)	0.13600 S 0.246	25	201 d WT% 3) 0.707 0	S.G. .874 0.4
Data Name File Name Sample Name Comment Entry Card D. Card	35. : CLIE : ALUM : ALUM e : : GREY Che Che Che Mo2C Moly Al203	57.4372 INT INIUM-BASE INIUM-BASE TISH SAMPLE mical Form mical Name bdenum Car	1.60309 .PSE ula (Mineral bide	11 Name)	0.13600 S 0.246 0.094	25 : L Dx 0.750(3/1	201 d WT% 3) 0.707 0 2) 0.797 0	S.G. .874 0.4
Data Name File Name Sample Name Comment Satry Card 0. Card 1 35-0787 2 10-0173	35. : CLIE : ALUM : ALUM e : : GREY Che Che Che Mo2C Mo1y Al203 Alum	57.4372 INT IINIUM-BASE IINIUM-BASE TISH SAMPLE mical Form mical Name bdenum Car inum Oxide	1.60309 .PSE ula (Mineral bide	11 Name)	0.13600 S 0.246 0.094	25 L Dx 0.750(3/1 0.556(5/4;	201 d WT% 3) 0.707 0 2) 0.797 0	S.G. .874 0.4 .697 0.3
Data Name File Name Sample Name Comment Satry Card 0. Card 1 35-0787 2 10-0173	35. : CLIE : ALUM : ALUM e : : GREY Che Che Che Mo2C Mo1y Al203 Alum NiFe204	57.4372 INT IINIUM-BASE IINIUM-BASE TISH SAMPLE mical Form mical Name bdenum Car inum Oxide	1.60309 .PSE (Mineral bide (Corundu	ii Name) um, syn	0.13600 S 0.246 0.094) 0.480	25 L Dx 0.750(3/1 0.556(5/4) 0.875(7/2)	201 d WT% 3) 0.707 0 2) 0.797 0	S.G. .874 0.4 .697 0.3
Data Name File Name Sample Name Comment Entry Card: 0. Card 1 35-0787 2 10-0173 3 10-0325	35. : CLIE : ALUM : ALUM : ALUM : GREY Che Che Che Moly Al203 Alum NiFe204 Nick	57.4372 INT IINIUM-BASE IINIUM-BASE IISH SAMPLE mical Form mical Name bdenum Car	1.60309 .PSE (Mineral bide (Corundu	ii Name) um, syn	0.13600 S 0.246 0.094) 0.480 syn)	25 L Dx 0.750(3/1 0.556(5/4: 0.875(7/2: .750(3/15)	201 d WT% 3) 0.707 0 2) 0.797 0 3) 0.701 0) 0.824 0.	S.G. .874 0.4 .697 0.3 .503 0.3 .431 0.26
Data Name File Name Sample Name Comment Entry Card 0. Card 1 35-0787 2 10-0173 3 10-0325 4 1-1236 F	35. : CLIE : ALUM : ALUM : ILUM : GREY Che Che Mo2C Mo12y Al203 Alum NiFe204 Nick 'e3N Iron	57.4372 NT HINIUM-BASE HINIUM-BASE HISH SAMPLE mical Form mical Form mical Name bdenum Car inum Oxide el Iron Ox Nitride	1.60309 .PSE (Mineral bide (Corundu	ii Name) um, syn	0.13600 S 0.246 0.094) 0.480 Syn) 0.166 0	25 L Dx 0.750(3/1) 0.555(5/4) 0.875(7/2) .750(3/15)	201 d WT% 3) 0.707 0 2) 0.797 0 3) 0.701 0	S.G. .874 0.4 .697 0.3 .503 0.3 .503 0.3 431 0.26
Data Name File Name Sample Name Comment Entry Card 0. Card 1 35-0787 2 10-0173 3 10-0325 4 1-1236 F	35. : CLIE : ALUM : ALUM : ALUM : GREY Che Che Che Moly Al203 Alum NiFe204 Nick Se3N Iron FeCr204	57.4372 NT HINIUM-BASE IINIUM-BASE IINIUM-BASE IINIUM-BASE MICAL FORM mical Name bdenum Car inum Oxide el Iron Ox Nitride	1.60309 .PSE (Mineral bide (Corundu ide (Trey	li Name) um, syn vorite,	0.13600 syn 0.246 0.094 0.480 syn 0.166 0 0.392	25 L Dx 0.750(3/1) 0.875(7/2) .750(3/15 0.857(6/2)	201 d WT% 3) 0.707 0 2) 0.797 0 3) 0.701 0) 0.824 0. 7) 0.576 0	S.G. .874 0.4 .697 0.3 .503 0.3 .503 0.3 431 0.26
Data Name File Name Sample Name Comment antry Card: c. Card 35-0787 2 10-0173 3 10-0325 10-0325 10-0325 11-1236 E	<pre>iss. i CLIE i ALUM i ALUM i ALUM i Che Che Mo2C Moly Al203 Alum NiFe204 Nick Fe3N Iron Fecr204 Iron</pre>	57.4372 NT HINIUM-BASE HINIUM-BASE HISH SAMPLE mical Form mical Form mical Name bdenum Car inum Oxide el Iron Ox Nitride	1.60309 .PSE (Mineral bide (Corundu ide (Trey	li Name) um, syn vorite,	0.13600 S 0.246 0.094) 0.480 Syn) 0.166 0 0.392 , syn)	25 L Dx 0.750(3/1 0.855(5/4) .750(3/15) 0.857(6/2)	d WT% 3) 0.707 0 2) 0.797 0 3) 0.701 0) 0.824 0. 7) 0.576 0	S.G. .874 0.4
Data Name File Name Sample Name Somment Intry Card: o. Card I 35-0787 2 10-0173 3 10-0325 4 1-1236 F 5 34-0140	<pre>i CLIE : ALUM : ALUM : ALUM : ALUM : GREY : GREY Che Che Moly Al203 Alum NiFe204 Nick Fe3N Iron FeCr204 Iron Fe2C</pre>	57.4372 NT INNUM-BASE UNUUM-BASE UNUUM-BASE SISH SAMPLE mical Form mical Form mical Form mical Form mical Form Mical Form Carbon Carbon Chromium	1.60309 .PSE (Mineral bide (Corundu ide (Trey	li Name) um, syn vorite,	0.13600 S 0.246 0.094) 0.480 Syn) 0.166 0 0.392 , syn)	25 L Dx 0.750(3/1) 0.556(5/4) 0.855(7/2) 0.857(6/2) 0.857(6/2) 0.750(3/1)	201 WT% 3) 0.707 0 2) 0.797 0 3) 0.701 0) 0.824 0. 7) 0.576 0 5) 0.859 0	S.G. .874 0.4
Data Name Pile Name Sample Name Comment Sontry Card Do Card 10-0173 10-0325 10-0325 11-1236 E 34-0140	is CLIE : ALUM : ALUM : ALUM : ALUM : GREY Che Che Che Che Che No2C Moly Aluco Alum NiFe2O4 NiFe2O4 Nick Fe3N Iron FeCr204 Iron Fe2C Iron	57.4372 NT HINIUM-BASE IINIUM-BASE IINIUM-BASE IINIUM-BASE MICAL FORM mical Name bdenum Car inum Oxide el Iron Ox Nitride	1.60309 .PSE (Mineral bide (Corundu ide (Trey	11 Name) worite,	0.13600 S 0.246 0.094) 0.480 syn) 0.166 0 0.392 , syn) 0.174	25 L Dx 0.750(3/1) 0.875(7/2) .750(3/15 0.857(6/2) 0.857(6/2)	d WT% 3) 0.707 0 2) 0.797 0 3) 0.701 0) 0.824 0. 7) 0.576 0 5) 0.859 0	S.G. .874 0.4 .697 0.3 .503 0.3 .431 0.26
Data Name Pile Name Sample Name Comment Sontry Card Do Card 10-0173 10-0325 10-0325 11-1236 E 34-0140	35. : CLIE : ALUM : ALUM : ALUM : GREY : GREY Che Che Moly Moly Moly Alum Nick Ye3N Iron FeCr204 Iron FeC2 Iron TiO2	57.4372 NT IINIUM-BASE UNIUM-BASE IINIUM-BASE Mical Form mical Form mical Form mical Form mical Form mical Form mical Form Nitride Chromium Carbide	1.60309 .PSE (Mineral bide (Corundu ide (Trev Oxide (Ch	11 Name) uum, syn vorite, nromite	0.13600 S 0.246 0.094) 0.166 0 0.392 , syn) 0.174 0.205	25 L Dx 0.750(3/1) 0.857(6/2) 0.857(6/2) 0.857(6/3)	d WT% 3) 0.707 0 2) 0.797 0 3) 0.701 0) 0.824 0. 7) 0.576 0 5) 0.859 0	S.G. .874 0.4 .697 0.3 .503 0.3 .431 0.26
Data Name File Name Sample Name Comment Shtry Card: Card 10-0173 10-0173 11-1236 F 11-1236 F 34-0140 34-0140	is CLIE : ALUM : ALUM : ALUM e : : GREY Che Che Che Che Che Che Moly Alum NiFe204 NiFe204 Nick Fe3N Iron FeCr204 Iron Fe2C Iron Tio2 Tita	57.4372 NT INNUM-BASE UNUUM-BASE UNUUM-BASE SISH SAMPLE mical Form mical Form mical Name bdenum Car inum Oxide chromium Carbide nium Oxide	1.60309 .PSE (Mineral bide (Corundu ide (Trey Oxide (Cl (Anatase	11 Name) uum, syn vorite, nromite	0.13600 0.246 0.094 0.480 syn) 0.166 0 0.392 , syn) 0.174 0.205)	25 L Dx 0.750(3/1) 0.556(5/4) 0.857(6/2) 0.857(6/2) 0.857(6/3)	d WT% 3) 0.707 0 2) 0.797 0 3) 0.701 0) 0.824 0. 7) 0.576 0 5) 0.859 0 3) 0.597 0	S.G. .874 0.4 .697 0.3 .503 0.3 431 0.26 .533 0.2 .396 0.2 .413 0.2
Data Name File Name Sample Name Comment Comment 1 35-0767 2 10-0173 3 10-0325 4 1-1236 F 5 34-0140 5 36-1249 7 21-1272	<pre>is cLIE is ALUM is ALUM is ALUM is ALUM is GREY Che Che Che Che Mo2C Moly All203 Alum NiFe204 Nick rean Iron Fecr204 Iron Fecr204 Iron Fe2C Iron Ti02 Ti12 NaAl2(A</pre>	57.4372 NT IINIUM-BASE UNIUM-BASE IINIUM-BASE IINIUM-BASE mical Name bdenum Car inum Oxide el Iron Ox Nitride Chromium Carbide nium Oxide 1533)010 (0)	1.60309 .PSE ula (Mineral bide (Corundu ide (Tree Oxide (Ch (Anatase H)2	11 Name) Name) vvorite, a, syn	0.13600 0.246 0.094 0.480 syn) 0.166 0 0.392 , syn) 0.174 0.205) 0.554	25 L Dx 0.750(3/1) 0.875(7/2) .750(3/1) 0.857(6/2) 0.857(6/2) 0.857(6/3) 0.857(6/3)	201 WT% 3) 0.707 0 2) 0.797 0 3) 0.701 0) 0.824 0. 7) 0.576 0 5) 0.859 0 9) 0.597 0 5) 0.804 0	S.G. .874 0.4 .697 0.3 .503 0.3 431 0.26 .533 0.2 .396 0.2 .413 0.2
Data Name File Name Sample Name Comment Sntry Card D. Card 1 0-0173 1 10-0325 1 10-0325 3 10-0325 3 4-0140 5 34-0140 5 36-1249 2 21-1272 2 24-1047	<pre>is clife is alum is alum is alum is alum che Moly alum NiFe204 Nick re3N Iron Fe2C Iron TiO2 Tita NaAl2(A Sod#</pre>	57.4372 NT IINIUM-BASE UNIUM-BASE IINIUM-BASE IINIUM-BASE mical Name bdenum Car inum Oxide el Iron Ox Nitride Chromium Carbide nium Oxide 1533)010 (0)	1.60309 .PSE ula (Mineral bide (Corundu ide (Tree Oxide (Ch (Anatase H)2	11 Name) Name) vorite, nromite e, syn	0.13600 0.13600 0.246 0.094 0.480 syn) 0.166 0 0.392 , syn) 0.174 0.205) 0.554 xide (Fa	25 L Dx 0.750(3/1 0.875(7/2) .750(3/15 0.857(6/2) 0.750(3/15 0.857(6/2) 0.750(3/15 0.857(6/2) 0.391(9/2) rag	201 WT% 3) 0.707 0 2) 0.797 0 3) 0.701 0 1) 0.824 0. 7) 0.576 0 5) 0.859 0 9) 0.597 0 5) 0.804 0	S.G. .874 0.4 .697 0.3 .503 0.3 .303 0.3 .334 0.26 .336 0.2 .413 0.2 .612 0.1
Data Name File Name Sample Name Comment Sntry Card D. Card 1 0-0173 1 10-0325 1 10-0325 3 10-0325 3 4-0140 5 34-0140 5 36-1249 2 21-1272 2 24-1047	<pre>iss. iss. iss. iss. iss. iss. iss. iss.</pre>	57.4372 NT INNUM-BASE UNUUM-BASE UNUUM-BASE ISH SAMPLE mical Form mical Form mical Form mical Form mical Form Mical Form Cal Form Carbide nium Oxide ISI3)010(iu mu Aluminu	1.60309 .PSE ula (Mineral bide (Corundu ide (Trev Oxide (Cl (Anatase H)2 m Silicate	li Name) uum, syn voorite, a, syn a Hydro	0.13600 0.13600 0.246 0.094 0.480 syn) 0.166 0 0.392 , syn) 0.174 0.205) 0.554 xide (Fa	25 L Dx 0.750(3/1) 0.556(5/4) 0.857(6/2) 0.857(6/2) 0.857(6/3) 0.857(6/3) 0.857(6/3) 0.857(6/3)	201 WT% 3) 0.707 0 2) 0.797 0 3) 0.701 0) 0.824 0. 7) 0.576 0 5) 0.859 0 3) 0.597 0 5) 0.804 0 0.506 0.	S.G. .874 0.4 .697 0.3 .503 0.3 .431 0.26 .533 0.2 .396 0.2 .413 0.2 .612 0.1
Data Name File Name Sample Name Comment Shtry Card D. Card 1 0-0173 1 10-0325 1 10-0325 1 1-1236 E 3 34-0140 5 36-1249 2 21-1272 2 21-1272 2 4-1047 6 6-0399 E	<pre>is clife clif</pre>	57.4372 NT IINIUM-BASE UNIUM-BASE IISH SAMPLE mical Name bdenum Car inum Oxide el Iron Ox Nitride Chromium • Carbide nium Oxide 1543)010 (0) um Aluminuu um Zirconiu	1.60309 .PSE ula (Mineral bide (Corundu ide (Trev Oxide (Cl (Anatase H)2 m Silicate	li Name) uum, syn voorite, a, syn a Hydro	0.13600 0.13600 0.246 0.094 0.480 syn) 0.166 0 0.392 , syn) 0.174 0.205) 0.554 xide (Pa 0.135 0	25 L Dx 0.750(3/1) 0.875(7/2) 0.875(7/2) 0.875(7/2) 0.857(6/2) 0.8	d WT% 3) 0.707 0 2) 0.797 0 3) 0.701 0 0 0.824 0. 7) 0.576 0 5) 0.859 0 9) 0.597 0 5) 0.804 0	S.G. .874 0.4 .697 0.3 .503 0.3 431 0.26 .533 0.2 .396 0.2 .413 0.2 .612 0.1 519 0.17
Data Name File Name Sample Name Comment Entry Card o. Card 1 35-0787 2 10-0173 3 10-0325 4 1-1236 f 5 34-0140 5 36-1249 7 21-1272 8 24-1047 0 6-0399 f	<pre>iss. iss. iss. iss. iss. iss. iss. iss.</pre>	57.4372 NT IINIUM-BASE IINIU	1.60309 .PSE ula (Mineral bide (Corundu ide (Trev (Anatase H)2 m Silicate um Oxide	lí Name) vvorite, anomite a, syn	0.13600 0.246 0.246 0.094 0.094 0.397 0.166 0 0.392 , syn) 0.174 0.205 0.554 xide (Pa 0.135 0 0.137	25 L Dx 0.750(3/1) 0.556(5/4) 0.875(7/2) .750(3/15 0.857(6/2) 0.750(3/15 0.857(6/2) 0.750(3/15 0.857(6/2) 0.391(9/2) rag .667(4/17) 0.452(14/3)	201 WT% 3) 0.707 0 2) 0.797 0 3) 0.701 0) 0.824 0. 7) 0.576 0 5) 0.859 0 9) 0.597 0 5) 0.804 0 4 0.506 0.1 1 0.712 0	s.G. .874 0.4 .697 0.3 .503 0.3 .431 0.26 .396 0.2 .413 0.2 .612 0.1 519 0.17 .498 0.1
	<pre>is clife clif</pre>	57.4372 NT IINIUM-BASE UNIUM-BASE IISH SAMPLE mical Name bdenum Car inum Oxide el Iron Ox Nitride Chromium • Carbide nium Oxide 1543)010 (0) um Aluminuu um Zirconiu	1.60309 .PSE ula (Mineral bide (Corundu ide (Trev (Anatase H)2 m Silicate um Oxide	lí Name) vvorite, anomite a, syn	0.13600 0.13600 0.246 0.094 0.166 0 0.392 , syn) 0.176 0.205) 0.205) 0.554 xide (Pa 0.135 0 0.197	25 L Dx 0.750(3/1) 0.875(7/2) 0.875(7/2) 0.875(7/2) 0.857(6/2) 0.8	201 WT% 3) 0.707 0 2) 0.797 0 3) 0.701 0) 0.824 0. 7) 0.576 0 5) 0.859 0 3) 0.597 0 5) 0.804 0 0.506 0. 1) 0.712 0 10	S.G. .874 0.4 .697 0.3 .503 0.3 .431 0.26 .533 0.2 .396 0.2 .413 0.2 .612 0.1 519 0.17 .498 0.1

Fig. 19. X-Ray Diffractometer (XRD) Analysis Result.

Element	Cu	Si	Mg	Zn	Fe	Mn	Ni	Ti	Cr
%	1.9924	16.182	5.6218	7.5650	0.75939	1.0102	3.0453	0.11968	0.50535
Sn	Pb	V	Р	Al	Ba				
0.16975	0.11760	0.10747	-	59.24	3.46				

Table 3. Optical Emission Spectrometer (OES) Analysis Result of the Aluminium Alloy Roofing SheetCovered with Dark-Black Material (Analysed at DICON, Kaduna).Parameter (in %)

Discussion. The method and the results of this work have been well presented and from the method it was established that the attachment of the dark-black material onto roof-tops is more of a physical thing than chemical. The deposits can be scrapped and it can also be cleaned with water and a soft brush without affecting the surface of the roofing sheets. The few growth of living things sighted occurred where the zinc coating on the roofing sheet had cracks. In such areas corrosion was also noticed. Other growths noticed on top of the deposits had no effect on the zinc coated roofing or the aluminium roofing sheets. This observation is in complete agreement with previous studies which had said that the presence of zinc, copper granules and aluminium salts discourages algae, fungal, moss and lichens growth [1], [4], [18]. According to InspectApedia.com [7], dark black or brown roof shingle stains are often caused by black algae, bleed-through or extractive bleeding of asphalt, dirt, soot, or organic debris. However, there are other roof stain colors and causes. Dangelo [4] said: "Just like wearing lighter colored clothing, a lighter colored shingle can reduce roof temperatures by 50 degrees or more". An added benefit is that white or light colored roofs benefit the environment as well. Dark-black stained roofs reduce the reflectiveness of roofs thereby making buildings to be hot requiring the use of air-conditioning systems.

The objective of this work is to understand the nature and characteristics of the dark-black stains on rooftops in Uyo metropolis. Water harvesting from rooftops is a common practice in Nigeria and therefore establishing the nature of this dark-black stains, which mixes with the water, is imperative. On this premise SEM micrographs were taken of the dark-black stains scrapped from the roof tops, dark-black stains on aluminium roofing sheet and dark-black stains on zinc coated roofing sheets (see Fig. 11-13). The micrographs (Fig. 11) which were taken at different magnifications revealed that the dark-black stains were not of uniform composition, but consisted of small white particles, amorphous-like molecular structure like that of the polymer material and a crystal-like structure similar to that seen in some carbon forms [8].

Chemical analysis using ED-XRF was carried out on the dark-black stains scrapped from the rooftops. The samples were sent to two different institutions for comparison so as to establish reliable result (see Tables 1-2). The dark-black stains from visual observation were sooty in nature. The two results have some compounds that are usually found in soot. The dark-black deposit is from the particulates in the air as well as the soot particles in the air. Gas flaring, the use of generators, and vehicular traffic releases emissions in the surrounding under study. The result from DICON Kaduna is higher than that from NMDC Jos in some of the parameters measured this may be because the analysis from DICON Kaduna did not take cognizance of organic, carbonaceous and volatile matter. The result from NMDC Jos however, assigned a total of 16.59% to this components. The result from NMDC Jos is therefore more reliable. In the two results the highest components of the dark-black stain powder scrapped from the roofs are SiO₂, Al₂O₃, Fe₂O₃, Carbonaceous and volatile organic matter, K₂O, TiO₂ and SO₃ see Tables 1-2 for detail percentages. Dara [3] said, that owing to particulates large surface areas, particulates provide excellent sites for absorption of various organic and inorganic species which encourage heterogeneous phase reactions in the atmosphere. Particulates include Fe₂O₃, V₂O₃, CaO, PbCl₂, PbBr₂, fly ash, aerosols, soot etc. polycyclic aromatic hydrocarbons (PAH) are important constituents of several organic particulates which are carcinogenic. Soot is a highly condensed product of PAH compounds and can itself adsorb many PAH compounds and toxic trace metals e.g Be, Cd, V, Ni, and Mn as well as carcinogenic organics such as benzo- α -pyrenes [3]. The last sentence agrees with the analysis results in Tables 1-2.

X-Ray Diffractometer (XRD) Analysis was also carried out on the dark black stains scrapped from the roof, dark-black stains on zinc substrate and dark-black stains on aluminium substrate, which were taken directly from the roofs (see Figs. 14-16). The X-Ray Diffractometer analysis of the scrapped dark black stains showed that in addition to the composition given by ED-XRF; the darkblack stains contained polytetrafluoroethylene, Calcium Fluoride, zinc phosphate hydrate, carbon (graphite) and magnesium. This result explains the structure seen in the SEM micrographs for the dark-black stains; the polytetrafluoroethylene may be responsible for the amorphous polymer structure seen and the carbon may be responsible for the carbon structure sighted in the SEM. The Zinc phosphate hydrate was scrapped along with the dark-black stains when samples were taken. This compound is normally at the surface of zinc coated roofing sheets. The XRD identification of components present in the dark black stains scrapped from roof-tops agreed with composition of soot and particulate as stated by [3].

The only new compounds in the analysis of the dark-black stains on zinc and aluminium substrate are chromium nitride, molybdenum carbide, and barium oxide. The chromium nitride indicate the presence of nitrogen. The molybdenum carbide indicate the presence of molybdenum on the substrate. The barium oxide indicate the presence of barium on the substrate. Table 3 which is the result of chemical analysis of the aluminium alloy roofing sheet using Optical Emission Spectrometer, confirms the presence of barium.

The above discussion have shown that the deposits on rooftops in Uyo metropolis are from particulates and soot. The health implications of these pollutants have been highlighted in the work by Okedere and Elehinafe who worked on the effect of suspended particulate matter from diesel generators. Other authors like Kirby [9], Mendez [10], Person and Kucera [14] have discussed rooftop stains and quality of water from the rooftops in their respective works. Of concern from the present study to health is SO₃, and polytetraflouroethylene which have health implications as shown by Dara [3], the other metals which are present in the dark black stains and also known to be associated with toxicity are actually in small quantities and may only cause problem over an extended period of exposure or usage of water from the roof tops.

Summary. The study titled "Understanding the Nature and Characteristics of Dark-Black Stains on Roof-Tops in Uyo Metropolis-Nigeria" was extensively and elaborately undertaken and considered to truly understand the true nature and characteristics of these dark black stains which have become an eye saw on rooftops in Uyo metropolis. The following findings and conclusions were drawn from the work:

1. The dark black stain/ covering on the rooftops is as a result of polluted atmosphere which is polluted with particulates, aerosols and soot these gets deposited on rooftops

2. The dark black stains are physically adsorbed or adhered to the roof and can be cleaned using water and soft brush.

3. The major components of the dark black stain are alumina, silica, carbonaceous and volatile organic matter, iron oxide (heamatite), potassium oxide, titanium oxide and sulphite (SO_3).

4. The dark black color is from the soot which contains carbon and other organic compounds and normally absorbs other particulates too. This explains the large compounds present in the dark black stain.

5. Finally, the wide range of tests carried out on the dark black stain on the rooftops have established that the components of health concern are SO_3 and the polytetrafluoroethylene. The other metallic components are in small quantities and may have health implication only after extended use of water from these rooftops. Acknowledgement. The authors of this work want to acknowledge the management of University of Uyo for approving this research work for TETFUND Institutional Research Grant without which this work would not have been possible. Our unreserved appreciation goes to the sponsors of this research work Tertiary Education Trust Fund, Abuja. We equally acknowledge institutions where this research work was carried out time will fail us to mention you by names again, since you have been earlier on mentioned in the work.

References

[1] Asanusung, K.E. (2014) Investigation of the possible causes of Aluminium Roofing Sheet Discolouration and its remedy: A Case Study of the University of Uyo Male Hostel Roof, Permanent Site, PGD Project, Department of Mechanical Engineering University of Uyo, Uyo, Nigeria.

[2] Bhatia, S.C.(2008) Environmental Chemistry, 4th Edition Reprint, published by Satish Kumar Jain for CBS Publishers & Distributors, Darya Ganj, New Delhi (India) p. 1-20.

[3] Dara, S.S. (2007) A Text book of Environmental Chemistry and Pollution Control, Seventh Reprint, S.Chand and Company Ltd, Ram Nagar New Delhi, p. 24-31.

[4] Dangelo, S. (2016), How White Roofs Can Help Your Home Cool, assessed at http://www.dangeloandson.com.

[5] Ihom, A.P. (2014) Environmental Pollution Prevention and Control: The Current Perspective (A Review), Journal of Multidisciplinary Engineering Science and Technology (JMEST), Vol. 1 Issue 5, 93-99.

[6] Ihom, A.P. and Offiong, A. (2014) Zinc-Plated Roofing Sheets and the Effect of Atmospheric Pollution on the Durability of the Sheets, Journal of Multidisciplinary Engineering Science and Technology (JMEST), Vol. 1, Issue 4, 125-132.

[7] Inspect Apedia (2017) Accessed at <u>www.InspectApedia.com</u>

[8] Katsnelson, I.M. (2007) Graphene: Carbon in Two Dimensions, Materials Today, vol. 10, No.1- 2, 20-27.

[9] Kirby, J.R. (1996) Cleaning, Preventing algae on asphalt shingles, National Rooting Contractors Association p.45, available at <u>www.nrca.net</u> accessed 2015.

[10] Mendez C.B., Afshar B.R., Kinney K., Barret M.E., Kirisits, M.J. (2010) Effect of Root Material on Water Quality for rainwater harvesting Systems. Texas Water Development board Report.

[11] Nkwocha, C.O. (2010) Environmental Impact of Oil and Gas Production in Nigeria, Journal of energy and power engineering, vol. 6, pp. 70-75.

[12] Ola, S.A., Salami, S.J., Ihom, P.A.(2013) The Levels of Toxic Gases; Carbon Monoxide, Hydrogen Sulphide and Particulate Matter to Index Pollution in Jos Metropolis, Nigeria, Journal of Atmospheric Pollution, Vol. 1, No. 1, 8-11.

[13] Olajire, A.A., Ayodele, E.T., Onyedirdan, G.O., Olugbemi, E.A. (2003) Levels and Specification of Heavy Metals in Soils of Industrial Southern Nigeria, Environmental Monitoring Assessment, Vol. 82(2), 135-155.

[14] Person, D. and Kucera, V. (2001) Release of Metals from Buildings, Constructions and Products during Atmospheric Exposure in Stockholm, Water, Air, and Solid Pollution Focus, 1(3), 133-150.

[15] E. A. Tice (1962) Effects of Air Pollution on the Atmospheric Corrosion Behavior of Some Metals and Alloys, Journal of the Air Pollution Control Association, 12:12, 553-559, DOI 10.1080/00022470.1962.10468127

[17] WHO (2014), WHO Report Worsening Air Quality in Cities. The Guardian Mobile, 7 May, 2014

[18] Woods, J. (2017) Reflective Surfaces (Geoengineering) Accessed at http://en.wikipedia.org/